

Electron-phonon coupling in 122 Fe pnictides analyzed by femtosecond time-resolved photoemission

L. Rettig^{1,2}, R. Cortés^{1,3}, H.S. Jeevan⁴, P. Gegenwart⁴, T. Wolf⁵, J. Fink⁶ and U. Bovensiepen²

¹Fachbereich Physik, Freie Universität Berlin, Arnimallee 14, D-14195 Berlin, Germany

²Fakultät für Physik, Universität Duisburg-Essen, Lotharstr. 1, D-47048 Duisburg, Germany

³Abt. Physikalische Chemie, Fritz-Haber-Institut d. MPG, Faradayweg 4-6, D-14195 Berlin, Germany

⁴I. Physik. Institut, Georg-August Universität Göttingen, D-37077 Göttingen, Germany

⁵Karlsruhe Institute of Technology, Institut für Festkörperphysik, D-76021 Karlsruhe, Germany

⁶Leibniz-Institute for Solid State and Materials Research Dresden, P.O.Box 270116, D-01171 Dresden, Germany

E-mail: uwe.bovensiepen@uni-due.de

Abstract. Based on results from femtosecond time-resolved photoemission, we compare three different methods for determination of the electron-phonon coupling constant λ in Eu and Ba-based 122 FeAs compounds. We find good agreement between all three methods, which reveal a small $\lambda < 0.2$. This makes simple electron-phonon mediated superconductivity unlikely in these compounds.

1. Introduction

Albeit an enormous amount of research has been conducted in the past few years on the Fe pnictide high-temperature superconductors (HTSCs) [1, 2], the search for the superconducting pairing mechanism in these materials is still ongoing. Besides other excitations such as spin fluctuations [3], the electron-phonon (e-ph) coupling responsible for Cooper pairing in conventional superconductors in the Bardeen-Cooper-Schrieffer (BCS) theory is considered a potential candidate. Therefore, the quantitative determination of the e-ph coupling constant λ in the Fe pnictides is of particular interest. Several methods to determine λ have been established in the literature and successfully used in various studies. In the energy domain, angle-resolved photoemission spectroscopy (ARPES) analyzes the renormalization of the single-particle spectral function by the electronic self energy Σ , which includes the e-ph coupling. However, such type of analysis requires very high sample and data quality, which is difficult to obtain in the Fe pnictides, and only few ARPES studies of FeAs compounds were able to determine effects of Σ [4, 5, 6]. In addition, in thermal equilibrium, contributions from other degrees of freedom to Σ are often difficult to disentangle from e-ph coupling.

In contrast, femtosecond (fs) time-resolved spectroscopies allow to separate e-ph scattering from other relaxation channels like e.g. electron-electron (e-e) scattering or heat diffusion due to their different intrinsic timescales out of thermal equilibrium [7, 8, 9]. Here, time-resolved ARPES (trARPES) is used, which combines the energy and momentum resolution of ARPES with fs time resolution into a powerful tool to directly investigate the dynamics of the electronic structure in a non-equilibrium state [10, 11].

The e-ph relaxation in metals after photoexcitation has been successfully described using the two-temperature model (2TM) [7, 8, 9, 12, 13, 14]. This model describes a system of two coupled heat baths for the conduction electrons and the ion lattice with temperatures T_e and T_l by coupled rate equations for T_e and T_l , respectively. One key assumption of this model is that e-e and phonon-phonon (ph-ph) scattering occurs on a much faster timescale than the e-ph scattering, leading to a thermal distribution within each subsystem. However, in correlated electron systems like the cuprate or Fe pnictide HTSCs, e-ph scattering might occur on similar timescales [15], which poses some questions on the applicability of the 2TM for these materials and care has to be taken. Therefore, we analyze our data in terms of a suitable version of the 2TM and compare the results with two complementary methods for the determination of the e-ph coupling strength. We find that all three methods to analyze the e-ph coupling strength from time-resolved photoemission data yield results for the second moment of the Eliashberg coupling function $\lambda \langle \omega^2 \rangle$ which agree well within error bars and reproduce the trends for three different 122 FeAs compounds consistently.

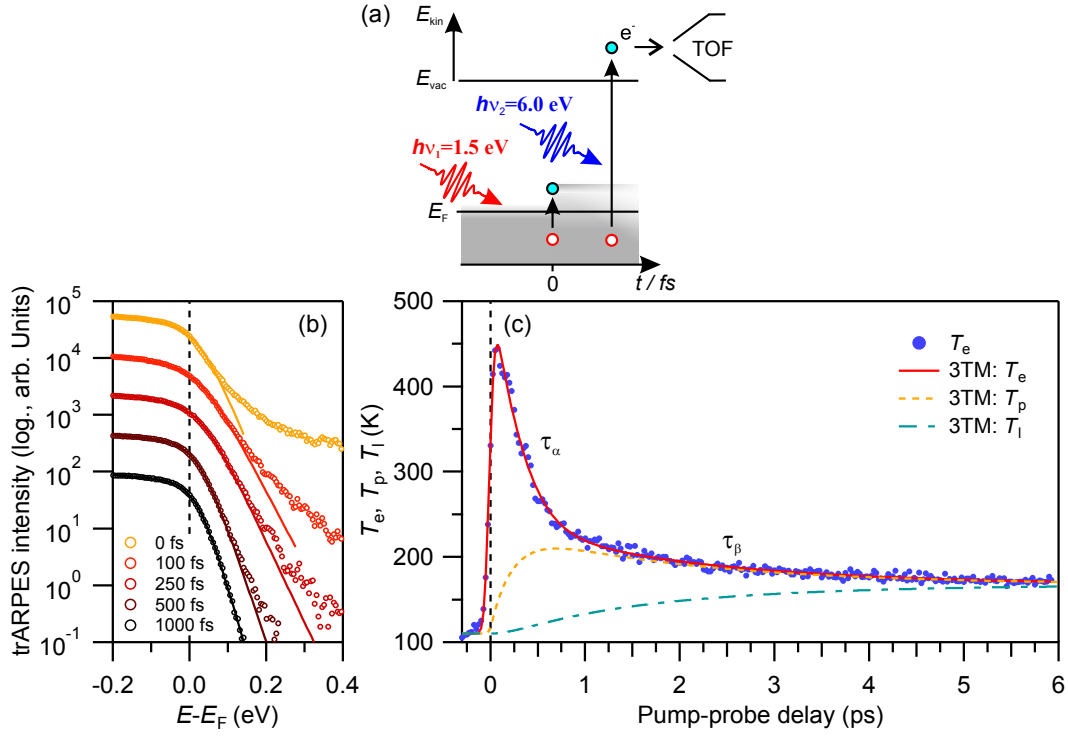


Figure 1. (a) Scheme of the pump-probe experiment. (b) Time-resolved ARPES spectra of EuFe_2As_2 at $T = 100$ K and at normal emission for various pump-probe delays on a logarithmic intensity scale using an incident pumping fluence of $F = 0.8 \text{ mJ/cm}^2$. Lines are fits to Fermi-Dirac distribution functions. (c) Electronic temperature T_e and a fit to the 3TM. Temperatures of the hot phonons (T_p) and the rest of the lattice modes (T_l) are shown as dashed and dash-dotted lines, respectively.

2. Experiments and results

For trARPES experiments, single crystals of EuFe_2As_2 and BaFe_2As_2 parent compounds and optimally doped $\text{BaFe}_{1.85}\text{Co}_{0.15}\text{As}_2$ ($T_c = 23$ K) were cleaved in ultrahigh vacuum ($p < 10^{-10}$ mbar) at $T = 100$ K where most measurements were carried out. The experimental setup is sketched in fig. 1(a): The output of a commercial regenerative Ti:Sapphire amplifier (Coherent RegA 9050) delivering ultrashort laser pulses at $h\nu_1 = 1.5$ eV photon energy with a pulse duration of 55 fs, and operating at 300 kHz is used to optically excite the samples (pump pulse). A time-delayed frequency-quadrupled probe pulse at $h\nu_2 = 6.0$ eV photon energy with a pulse duration of 80 fs leads to the emission of photoelectrons, which are detected using an electron time-of-flight (TOF) spectrometer with an acceptance angle of $\pm 3^\circ$. The energy resolution of 50 meV is mainly determined by the spectral width of the probe pulses, and the overall temporal resolution is < 100 fs. For details see [9].

2.1. Three-Temperature model

Exemplary trARPES data of EuFe_2As_2 are shown in fig. 1(b) for various pump-probe delays on a logarithmic intensity scale. After excitation, a pronounced distribution of excited charge carriers is formed at $E - E_F > 0.1 \text{ eV}$, which deviates from the Fermi-Dirac distribution of the electronic system before excitation and which originates from hot, non-thermalized electrons. Subsequently, e-e scattering quickly leads to thermalization of these non-thermal electrons and to the formation of a hot thermalized electron distribution [9]. At $t > 250 \text{ fs}$, the non-thermal contribution has decayed to less than 1% of the electron population.

The temperature of the thermalized part of the electronic system T_e can be extracted from the trARPES data by fitting a Fermi-Dirac distribution function to the high-energy cutoff of the transient spectra, multiplied by a phenomenological density-of-states function and convoluted with an instrumental resolution function [9, 14], as shown in fig. 1(b) (solid lines). T_e determined by the fitting is shown in fig. 1(c) as a function of pump-probe delay. After the steep rise of the electronic temperature at zero pump-probe delay, we find a relaxation on two distinct timescales τ_α and τ_β . Such a behavior indicates the selective coupling of hot electrons to a subset of strongly coupled phonon modes on the faster timescale τ_α and the subsequent energy transfer to the rest of the phonons by anharmonic ph-ph scattering, determined by τ_β . Thus, the system is described by an extended version of the 2TM, which had been developed for the cuprate HTSCs [14], where a similar relaxation dynamics was found, and which has been also used recently for the Fe pnictides [16, 17]. This three-temperature model (3TM) consists of a system of three coupled differential equations describing the temperature of the electrons, T_e , of a hot phonon distribution T_p and of the rest of the lattice modes, T_l :

$$\frac{dT_e}{dt} = -H(T_e, T_p) + \frac{S}{C_e} \quad (1)$$

$$\frac{dT_p}{dt} = +\frac{C_e}{C_p}H(T_e, T_p) - \frac{T_p - T_l}{\tau_\beta} \quad (2)$$

$$\frac{dT_l}{dt} = +\frac{C_p}{C_l}\frac{T_p - T_l}{\tau_\beta} \quad (3)$$

The source term S describes the optical excitation, C_e , C_p and C_l are the specific heat capacities of electrons, strongly and weakly coupled phonon modes, respectively. The anharmonic decay of phonons is described by τ_β . For the energy transfer from the electrons to the more strongly coupled phonons, the formula derived by Allen [7] is used:

$$H(T_e, T_p) = \gamma_T(T_e - T_p) = \frac{3\hbar\lambda\langle\omega^2\rangle}{\pi k_B} \frac{T_e - T_p}{T_e}, \quad (4)$$

where k_B is the Boltzmann constant. This relation allows determination of the second moment of the Eliashberg e-ph coupling function $\lambda\langle\omega^2\rangle$.

A fit of a numerical solution of the 3TM to T_e is shown in fig. 1(c) and yields a good agreement to the experimental data. Due to an ambiguity of the model parameters such as the electron and lattice specific heat capacities reported in the literature, a

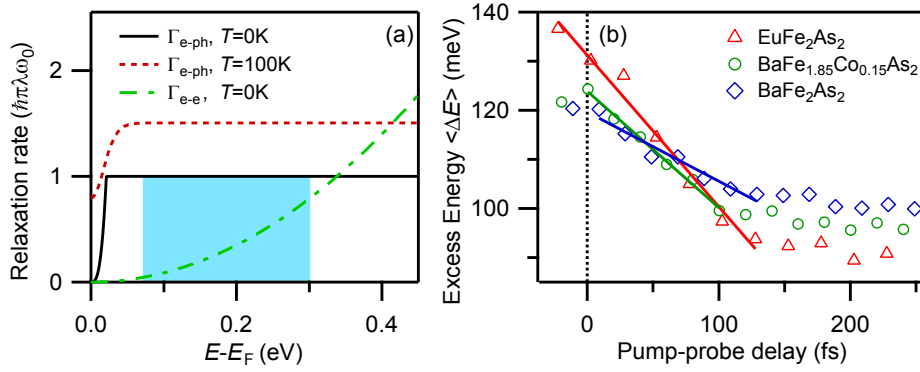


Figure 2. (a) e-ph and e-e contributions to the electron decay rate Γ . The e-ph contribution Γ_{e-ph} calculated in the Debye model with $\hbar\omega_D = 20$ meV and $\lambda = 0.3$ at $T = 0$ K and $T = 100$ K increases up to $\sim \omega_D$ and is constant above. The electronic contribution Γ_{e-e} calculated for $\beta = 0.1 \text{ eV}^{-1}$ exceeds Γ_{e-ph} only at higher energies. The shaded area marks the energy where e-ph scattering dominates. (b) Electron mean excess energy extracted from trARPES data at $T = 100$ K near k_F within the energy window $0.07 \text{ eV} < \epsilon < 0.3 \text{ eV}$ marked in (a). Solid lines are fits to equation (6).

range of values for $\lambda \langle \omega^2 \rangle$ is retrieved, where the fits show similar good agreement to the data. Details of this analysis can be found in [17]; here, only the main results are discussed. From the 3TM, we find values of $\lambda \langle \omega^2 \rangle = 56 - 65 \text{ meV}^2$ for EuFe_2As_2 , while in $\text{BaFe}_{1.85}\text{Co}_{0.15}\text{As}_2$ it is slightly smaller ($\lambda \langle \omega^2 \rangle = 46 - 55 \text{ meV}^2$) and even smaller in undoped BaFe_2As_2 ($\lambda \langle \omega^2 \rangle = 30 - 46 \text{ meV}^2$).

2.2. Electronic excess energy

The analysis within the 3TM was based on the energy relaxation within the thermalized part of the transient electronic distribution function and thus neglected the non-thermal electrons present at early delay times (see fig. 1(b)). However, the analysis of the energy relaxation of these non-thermal, excited electrons can also provide information about the strength of e-ph coupling.

The scattering rate of electrons excited at energy $\epsilon = E - E_F$ above the Fermi level is in the self-energy formulation of many-body theory determined by $\Gamma = \hbar\tau^{-1} = 2\text{Im}\Sigma(\epsilon)$, where $\text{Im}\Sigma$ is the imaginary part of the electronic self energy [18]. Important energy-dependent contributions to Γ arise from e-e and e-ph scattering, where e-e scattering is considered to follow the quadratic energy scaling of the Fermi liquid theory, $\Gamma_{e-e} = 2\beta [(\pi k_B T)^2 + \epsilon^2]$ (fig. 2(a)). As the proportionality coefficient β is rather small in typical metals (in the order of 10^{-2} eV^{-1} to 10^{-1} eV^{-1}) [19, 20], this contribution is negligible compared to the e-ph scattering at low enough excitation energies. The latter increases up to the maximal phonon energy $\hbar\omega_{max}$ and is constant above (fig. 2(a)). For $\epsilon > \hbar\omega_{max}$ and $T = 0$ K, Γ_{e-ph} results for an Einstein mode ω_0 to [21]

$$\Gamma_{e-ph} = \pi \hbar \lambda \omega_0 \quad . \quad (5)$$

Within the energy window between $\hbar\omega_{max}$ and the crossover regime, where Γ_{e-e} becomes dominant (shaded area in fig. 2(a)), the rate of energy dissipation of an electron due to the emission of a phonon with energy $\hbar\omega_0$ is given by

$$\frac{dE}{dt} = \frac{\hbar\omega_0}{\tau} = \pi\hbar\lambda\omega_0^2 \quad , \quad (6)$$

which leads to a linear relaxation of the electron energy [22].

The rate of energy relaxation of excited electrons can be extracted from the experimental trARPES intensity $I(\epsilon, t)$ by analyzing the mean excess energy,

$$\langle\Delta E(t)\rangle = \frac{\int_{\epsilon_0}^{\epsilon_1} \epsilon \Delta I(\epsilon, t) d\epsilon}{\int_{\epsilon_0}^{\epsilon_1} \Delta I(\epsilon, t) d\epsilon} \quad . \quad (7)$$

However, this integral represents the mean excess energy within a selected partition of a transient distribution function and not the energy relaxation of single individual electrons. Thus, special care has to be taken with the determination of the integration boundaries, ϵ_0 and ϵ_1 . A careful investigation of the influence of the integration boundaries and the excitation fluence reveals that a reasonable choice of $\epsilon_0 = 70$ meV and $\epsilon_1 = 300$ meV allows to give a good estimate of the e-ph coupling strength, as detailed in [23].

Experimental data of EuFe_2As_2 , $\text{BaFe}_{1.85}\text{Co}_{0.15}\text{As}_2$ and BaFe_2As_2 near k_F and at $T = 100$ K are shown in fig. 2(b). To minimize lattice heating and the influence of the hot thermalized electron distribution, low excitation fluences of $F \sim 50 \mu\text{Jcm}^{-2}$ have been used. The linear fits to equation (6) within the first 100 fs yield values of $\lambda\langle\omega^2\rangle = 65(5) \text{ meV}^2$ for EuFe_2As_2 , $50(3) \text{ meV}^2$ for $\text{BaFe}_{1.85}\text{Co}_{0.15}\text{As}_2$ and $34(6) \text{ meV}^2$ for BaFe_2As_2 . Here, error bars represent the numerical uncertainties of the fits, while the overall errors have to be considered larger due to the uncertainty of the integration boundaries discussed above and of the elevated lattice temperature. Nevertheless, we find a good agreement with the values obtained in the 3TM simulations and a considerably higher e-ph coupling in EuFe_2As_2 than in $\text{BaFe}_{1.85}\text{Co}_{0.15}\text{As}_2$ and even lower $\lambda\langle\omega^2\rangle$ in BaFe_2As_2 .

2.3. Temperature-dependent hole relaxation rates

Finally, another estimate of the e-ph coupling strength can be gained from the temperature dependence of quasiparticle (QP) relaxation rates [7, 15, 24, 25]. A recent theoretical investigation of the Boltzmann equation for e-e and e-ph interaction found an analytic solution for the temperature dependence of the QP relaxation rate τ [24]. In the limit of a bad metal at elevated temperatures, τ depends linearly on the lattice temperature T [15, 24, 25]:

$$\tau = \frac{2\pi k_B T}{3\hbar\lambda\langle\omega^2\rangle} \quad . \quad (8)$$

This relation allows for an independent determination of the e-ph coupling strength $\lambda\langle\omega^2\rangle$.

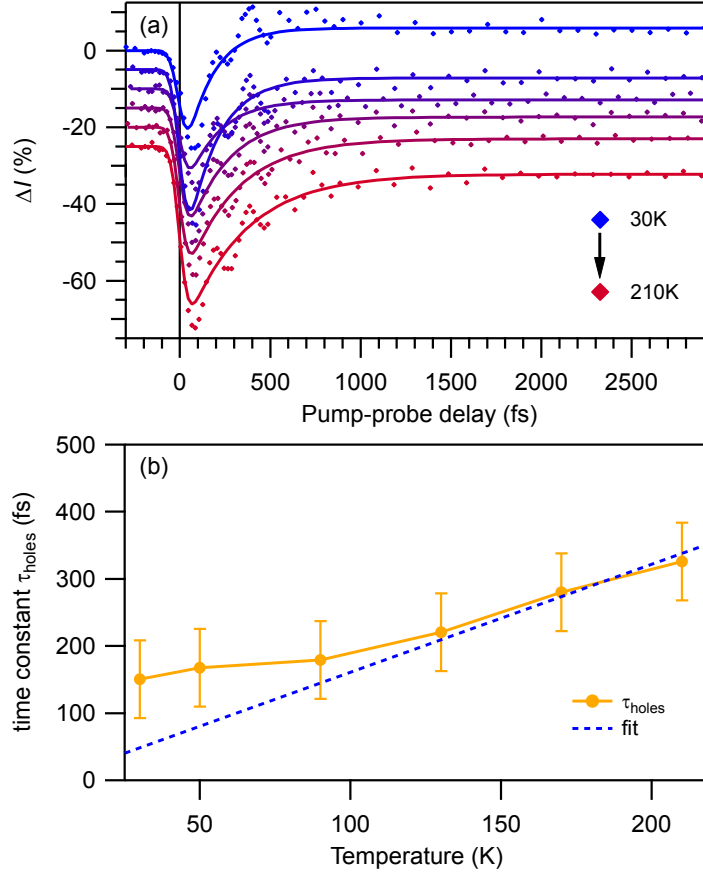


Figure 3. Evaluation of the temperature dependence of relaxation rates in EuFe_2As_2 . (a) Time-dependent spectral weight of holes at $k_{\parallel} > k_F$ for various temperatures. Data are vertically offset for clarity. Solid lines are exponential fits (see text). (b) Relaxation time constants τ_{holes} determined from the data in (a) as function of temperature. The dashed line is a fit to equation (8) in the temperature range $T > 100\text{K}$.

Experimentally, the temperature-dependent relaxation of holes in the hole pocket near Γ in EuFe_2As_2 are used, which are found to be independent from the antiferromagnetic transition [26]. The respective hole relaxation time τ_{holes} is determined from the temperature-dependent trARPES intensity by fitting exponential decay curves (fig. 3(a)) and is shown in fig. 3(b) as a function of temperature. The fit to equation (8) for $T > 100\text{K}$ reveals a good agreement to the linear behavior and yields a value of $\lambda \langle \omega^2 \rangle = 90(30) \text{ meV}^2$, where the error represents a confidence interval of 80%. This value, albeit considerably higher than the values found in the 3TM and in the evaluation of the excess energy, is in agreement with the other evaluations within error bars.

3. Discussion

The values of $\lambda \langle \omega^2 \rangle$ determined by the three methods discussed above are compared in table 1. Despite the limitations and drawbacks of the various methods, we find a perfect

Table 1. Values of $\lambda \langle \omega^2 \rangle$ determined by the three methods.

compound	$T_c(t)$	$\langle \Delta E(t) \rangle$	$\tau_{\text{holes}}(t)$
EuFe ₂ As ₂	56 – 65	65(5)	90(30)
BaFe _{1.85} Co _{0.15} As ₂	46 – 55	50(3)	-
BaFe ₂ As ₂	30 – 46	34(6)	-

agreement of all three methods within error bars. Especially, the trend for larger e-ph coupling in EuFe₂As₂ than in BaFe_{1.85}Co_{0.15}As₂ and in BaFe₂As₂ is nicely represented. Remarkably, all methods produce a small $\lambda \langle \omega^2 \rangle < 100 \text{ meV}^2$, which already indicates weak e-ph coupling.

Our values of $\lambda \langle \omega^2 \rangle$ can be compared to recently published values determined from optical pump-probe experiments. Mansart *et al.* [16] report a comparable value of $\lambda \langle \omega^2 \rangle \approx 64 \text{ meV}^2$ for Co-doped BaFe₂As₂, which was determined using the 3TM. Stojchevska *et al.* [25] derived a somewhat higher value of $\lambda \langle \omega^2 \rangle = 110(10) \text{ meV}^2$ in SrFe₂As₂ using temperature-dependent QP relaxation times, and for SmFeAsO_{1-x}F_x an even larger value of $\lambda \langle \omega^2 \rangle = 135(10) \text{ meV}^2$ is reported [27].

Based on our results of $\lambda \langle \omega^2 \rangle$ we can estimate the value of the e-ph coupling constant λ for a particular value of ω . Considering the Raman active A_{1g} mode at 23 meV, which can be coherently excited [17, 28, 29] and therefore shows enhanced e-ph coupling in the system, we find $\lambda < 0.2$ for all compounds. This estimate is in agreement with calculations of various Fe-pnictide compounds, which report values of $\lambda < 0.35$ [30, 31]. Taking the mean of the phonon spectrum as reference, λ gets even smaller, in agreement with other publications [16, 25]. Even if we consider the lowest coupled modes around 12 meV to be most important for e-ph coupling, λ does not exceed a value of 0.5. Similarly small values for λ have been found in the cuprate HTSCs [14, 15], which suggests limited importance of e-ph coupling for the pairing mechanism in both classes of materials.

These boundaries for the e-ph coupling constant λ allow to estimate the superconducting critical temperature T_c , assuming a conventional BCS-type pairing based on e-ph coupling. Here, T_c in isotropic systems and in a strong coupling regime is given by McMillan's formula [32], modified by Allen and Dynes [33],

$$T_c = \frac{\omega_{\log}}{1.20} \exp \left(-\frac{1.04(1 + \lambda)}{\lambda - \mu^* - 0.62\lambda\mu^*} \right) \quad (9)$$

where μ^* is the effective Coulomb repulsion and ω_{\log} is the logarithmic average of the phonon spectrum. Taking $\mu^* = 0$ and $\omega_{\log} = 205 \text{ K}$ [30], which provides an upper limit for T_c , we find $T_c = 0.33 \text{ K}$ and $T_c = 7.5 \text{ K}$ for $\lambda = 0.2$ and $\lambda = 0.5$, respectively. Comparing these results with the experimentally found $T_c = 24 \text{ K}$ in optimally doped BaFe_{1.85}Co_{0.15}As₂ [34] and even up to $T_c = 38 \text{ K}$ in K doped BaFe₂As₂ [35] demonstrates

that e-ph coupling in a conventional BCS pairing scenario cannot explain the high critical temperatures found in the pnictide HTSCs. In addition, albeit the stronger e-ph coupling, the critical temperatures found in EuFe_2As_2 upon Co [36] and K [37] substitution are considerably smaller compared to BaFe_2As_2 .

However, e-ph coupling might still play a significant role in the Cooper pair formation in the Fe pnictides. For instance, a very strong sensitivity of the Fe magnetic moment on the As height in the FeAs tetrahedra was found in DFT band structure calculations [38], with a rate of $6.8 \mu_B/\text{\AA}$. Inelastic x-ray scattering experiments on CaFe_2As_2 concluded on strong coupling of phonons to magnetic excitations even in the high-temperature paramagnetic phase [39]. Furthermore, a strong sensitivity of the maximum critical temperature on the pnictogen height was found [1]. On the basis of these findings a strong magneto-phonon coupling in these compounds was proposed and, e.g. the strongly coupled A_{1g} mode perpendicular to the Fe layers, which modulates the pnictogen height, could mediate superconductivity in the Fe-pnictides [40]. Such a scenario is supported by the strong coupling of this particular mode to electronic states directly at the Fermi level [17] evidenced by the coherent excitation of this phonon mode [17, 28, 29].

4. Summary

In summary, we demonstrated the quantitative analysis of the e-ph coupling strength from femtosecond time- and angle-resolved photoemission spectroscopy. In detail, we compared three different methods to determine the e-ph coupling strength in three 122 FeAs compounds from time- and angle-resolved photoemission experiments. The transient temperature of the thermalized electronic distribution is analyzed in EuFe_2As_2 , $\text{BaFe}_{1.85}\text{Co}_{0.15}\text{As}_2$ and BaFe_2As_2 by a three-temperature model, while the rate of energy relaxation of the non-thermal electrons yields direct information on the second moment of the Eliashberg coupling function $\lambda \langle \omega^2 \rangle$. Finally, the temperature-dependence of hole relaxation rates in EuFe_2As_2 also allows to determine $\lambda \langle \omega^2 \rangle$. All three methods consistently yield a small $\lambda \langle \omega^2 \rangle < 100 \text{ meV}^2$, which results in $\lambda < 0.2$ using a reasonable choice of the phonon spectrum. This value is discussed to be too small to explain superconductivity in the Fe pnictides by a conventional BCS-type pairing.

5. Acknowledgements

Experiments were carried out at the Freie Universität Berlin. We acknowledge discussions with Martin Wolf and Hermann Dürr in the early stage of the project and experimental support by Setti Thirupathaiah. This work was supported by the Mercator Research Center Ruhr and the Deutsche Forschungsgemeinschaft through BO 1823/2 and SPP 1458. R.C. acknowledges the Alexander von Humboldt Foundation.

6. References

- [1] D. C. Johnston. The puzzle of high temperature superconductivity in layered iron pnictides and chalcogenides. *Adv. Phys.*, 59:803, 2010.
- [2] G. R. Stewart. Superconductivity in iron compounds. *Rev. Mod. Phys.*, 83:1589, 2011.
- [3] I. I. Mazin, D. J. Singh, M. D. Johannes, and M. H. Du. Unconventional Superconductivity with a Sign Reversal in the Order Parameter of $\text{LaFeAsO}_{1-x}\text{F}_x$. *Phys. Rev. Lett.*, 101:057003, 2008.
- [4] L. Wray, D. Qian, D. Hsieh, et al. Momentum dependence of superconducting gap, strong-coupling dispersion kink, and tightly bound Cooper pairs in the high- T_c $\text{SrBa}_{1-x}(\text{K,Na})_x\text{Fe}_2\text{As}_2$ superconductors. *Phys. Rev. B*, 78:184508, 2008.
- [5] P. Richard, T. Sato, K. Nakayama, S. Souma, T. Takahashi, Y.-M. Xu, G. F. Chen, J. L. Luo, N. L. Wang, and H. Ding. Angle-Resolved Photoemission Spectroscopy of the Fe-Based $\text{Ba}_{0.6}\text{K}_{0.4}\text{Fe}_2\text{As}_2$ High Temperature Superconductor: Evidence for an Orbital Selective Electron-Mode Coupling. *Phys. Rev. Lett.*, 102:047003, 2009.
- [6] A. Koitzsch, D. S. Inosov, D. V. Evtushinsky, V. B. Zabolotnyy, A. A. Kordyuk, A. Kondrat, C. Hess, M. Knupfer, B. Büchner, G. L. Sun, V. Hinkov, C. T. Lin, A. Varykhalov, and S. V. Borisenko. Temperature and Doping-Dependent Renormalization Effects of the Low Energy Electronic Structure of $\text{Ba}_{1-x}\text{K}_x\text{Fe}_2\text{As}_2$ Single Crystals. *Phys. Rev. Lett.*, 102:167001, 2009.
- [7] P. B. Allen. Theory of thermal relaxation of electrons in Metals. *Phys. Rev. Lett.*, 59:1460, 1987.
- [8] N. Del Fatti, C. Voisin, M. Achermann, S. Tzortzakis, D. Christofilos, and F. Vallée. Nonequilibrium electron dynamics in noble metals. *Phys. Rev. B*, 61:16956, 2000.
- [9] M. Lisowski, P. A. Loukakos, U. Bovensiepen, J. Stähler, C. Gahl, and M. Wolf. Ultra-fast dynamics of electron thermalization, cooling and transport effects in $\text{Ru}(001)$. *Appl. Phys. A*, 78:165, 2004.
- [10] U. Bovensiepen, H. Petek, and M. Wolf, editors. *Dynamics at Solid State Surfaces and Interfaces, Vol. 1*. Wiley-VCH Weinheim, Germany, 2010.
- [11] U. Bovensiepen and P. S. Kirchmann. Elementary relaxation processes investigated by femtosecond photoelectron spectroscopy of two-dimensional materials. *Laser & Photonics Reviews*, 6(5):589, 2012.
- [12] S. I. Anisimov, B. L. Kapeliovich, and T. L. Perelman. Electron Emission from Metal Surfaces Exposed to Ultrashort Laser Pulses. *Sov. Phys. JETP-USSR*, 39:375, 1974.
- [13] B. Rethfeld, A. Kaiser, M. Vicanek, and G. Simon. Ultrafast Dynamics of Nonequilibrium Electrons in Metals Under Femtosecond Laser Irradiation. *Phys. Rev. B*, 65:214303, 2002.
- [14] L. Perfetti, P. A. Loukakos, M. Lisowski, U. Bovensiepen, H. Eisaki, and M. Wolf. Ultrafast electron relaxation in superconducting $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$ by time-resolved photoelectron spectroscopy. *Phys. Rev. Lett.*, 99:197001, 2007.
- [15] C. Gadermaier, A. S. Alexandrov, V. V. Kabanov, P. Kusar, T. Mertelj, X. Yao, C. Manzoni, D. Brida, G. Cerullo, and D. Mihailovic. Electron-Phonon Coupling in High-Temperature Cuprate Superconductors Determined from Electron Relaxation Rates. *Phys. Rev. Lett.*, 105:257001, 2010.
- [16] B. Mansart, D. Boschetto, A. Savoia, F. Rullier-Albenque, F. Bouquet, E. Papalazarou, A. Forget, D. Colson, A. Rousse, and M. Marsi. Ultrafast transient response and electron-phonon coupling in the iron-pnictide superconductor $\text{Ba}(\text{Fe}_{1-x}\text{Co}_x)_2\text{As}_2$. *Phys. Rev. B*, 82:024513, 2010.
- [17] I. Avigo, R. Corts, L. Rettig, S. Thirupathaiah, H. S. Jeevan, P. Gegenwart, T. Wolf, M. Ligges, M. Wolf, J. Fink, and U. Bovensiepen. Coherent excitations and electron-phonon coupling in $\text{Ba}/\text{EuFe}_2\text{As}_2$ compounds investigated by femtosecond time- and angle-resolved photoemission spectroscopy. *J. Phys.: Condens. Matter*, 25(9):094003, 2013.
- [18] P. M. Echenique, J. M. Pitarke, E. V. Chulkov, and A. Rubio. Theory of Inelastic Lifetimes of Low-Energy Electrons in Metals. *Chem. Phys.*, 251:1, 2000.
- [19] B. A. McDougall, T. Balasubramanian, and E. Jensen. Phonon contribution to quasiparticle lifetimes in Cu measured by angle-resolved photoemission. *Phys. Rev. B*, 51:13891, 1995.

- [20] T. Valla, A. V. Fedorov, P. D. Johnson, and S. L. Hulbert. Many-body effects in angle-resolved photoemission: Quasiparticle energy and lifetime of a Mo(110) surface state. *Phys. Rev. Lett.*, 83:2085, 1999.
- [21] S. Engelsberg and J. R. Schrieffer. Coupled Electron-Phonon System. *Phys. Rev.*, 131:993, 1963.
- [22] V. E. Gusev and O. B. Wright. Ultrafast nonequilibrium dynamics of electrons in metals. *Phys. Rev. B*, 57:2878, 1998.
- [23] L. Rettig. *Ultrafast Dynamics of Correlated Electrons*. PhD thesis, Freie Universität Berlin, 2012.
- [24] V. V. Kabanov and A. S. Alexandrov. Electron relaxation in metals: Theory and exact analytical solutions. *Phys. Rev. B*, 78:174514, 2008.
- [25] L. Stojchevska, P. Kusar, T. Mertelj, V. V. Kabanov, X. Lin, G. H. Cao, Z. A. Xu, and D. Mihailovic. Electron-phonon coupling and the charge gap of spin-density wave iron-pnictide materials from quasiparticle relaxation dynamics. *Phys. Rev. B*, 82:012505, 2010.
- [26] L. Rettig, R. Cortés, S. Thirupathaiah, P. Gegenwart, H. S. Jeevan, M. Wolf, J. Fink, and U. Bovensiepen. Ultrafast Momentum-Dependent Response of Electrons in Antiferromagnetic EuFe_2As_2 Driven by Optical Excitation. *Phys. Rev. Lett.*, 108:097002, 2012.
- [27] T. Mertelj, P. Kusar, V. V. Kabanov, L. Stojchevska, N. D. Zhigadlo, S. Katrych, Z. Bukowski, J. Karpinski, S. Weyeneth, and D. Mihailovic. Quasiparticle relaxation dynamics in spin-density-wave and superconducting $\text{SmFeAsO}_{1-x}\text{F}_x$ single crystals. *Phys. Rev. B*, 81:224504, 2010.
- [28] B. Mansart, D. Boschetto, A. Savoia, F. Rullier-Albenque, A. Forget, D. Colson, A. Rousse, and M. Marsi. Observation of a coherent optical phonon in the iron pnictide superconductor $\text{Ba}(\text{Fe}_{1-x}\text{Co}_x)_2\text{As}_2$ ($x = 0.06$ and 0.08). *Phys. Rev. B*, 80:172504, 2009.
- [29] K. W. Kim, A. Pashkin, H. Schäfer, M. Beyer, M. Porer, T. Wolf, C. Bernhard, J. Demsar, R. Huber, and A. Leitenstorfer. Ultrafast transient generation of spin-density-wave order in the normal state of BaFe_2As_2 driven by coherent lattice vibrations. *Nat. Mater.*, 11:497, 2012.
- [30] L. Boeri, O. V. Dolgov, and A. A. Golubov. Is $\text{LaFeAsO}_{1-x}\text{F}_x$ an Electron-Phonon Superconductor? *Phys. Rev. Lett.*, 101:026403, 2008.
- [31] L. Boeri, M. Calandra, I. I. Mazin, O. V. Dolgov, and F. Mauri. Effects of magnetism and doping on the electron-phonon coupling in BaFe_2As_2 . *Phys. Rev. B*, 82:020506, 2010.
- [32] W. L. McMillan. Transition Temperature of Strong-Coupled Superconductors. *Phys. Rev.*, 167:331, 1968.
- [33] P. B. Allen and R. C. Dynes. Transition temperature of strong-coupled superconductors reanalyzed. *Phys. Rev. B*, 12:905, 1975.
- [34] J.-H. Chu, J. G. Analytis, C. Kucharczyk, and I. R. Fisher. Determination of the phase diagram of the electron-doped superconductor $\text{Ba}(\text{Fe}_{1-x}\text{Co}_x)_2\text{As}_2$. *Phys. Rev. B*, 79:014506, 2009.
- [35] M. Rotter, M. Tegel, D. Johrendt, I. Schellenberg, W. Hermes, and R. Pöttgen. Spin-density-wave anomaly at 140 K in the ternary iron arsenide bafe_2as_2 . *Phys. Rev. B*, 78:020503, 2008.
- [36] S. Jiang, H. Xing, G. Xuan, Z. Ren, C. Wang, Z.-a. Xu, and G. Cao. Superconductivity and local-moment magnetism in $\text{Eu}(\text{Fe}_{0.89}\text{Co}_{0.11})_2\text{as}_2$. *Phys. Rev. B*, 80:184514, 2009.
- [37] Anupam, P. L. Paulose, S. Ramakrishnan, and Z. Hossain. Doping dependent evolution of magnetism and superconductivity in $\text{Eu}_{1-x}\text{K}_x\text{Fe}_2\text{As}_2$ ($x=0-1$) and temperature dependence of the lower critical field H_{c1} . *J. Phys.: Condens. Matter*, 23:455702, 2011.
- [38] Z. P. Yin, S. Lebègue, M. J. Han, B. P. Neal, S. Y. Savrasov, and W. E. Pickett. Electron-Hole Symmetry and Magnetic Coupling in Antiferromagnetic LaFeAsO . *Phys. Rev. Lett.*, 101:047001, 2008.
- [39] S. E. Hahn, Y. Lee, N. Ni, P. C. Canfield, A. I. Goldman, R. J. McQueeney, B. N. Harmon, A. Alatas, B. M. Leu, E. E. Alp, D. Y. Chung, I. S. Todorov, and M. G. Kanatzidis. Influence of magnetism on phonons in CaFe_2As_2 as seen via inelastic x-ray scattering. *Phys. Rev. B*, 79:220511, 2009.
- [40] T. Egami, B. V. Fine, D. Parshall, A. Subedi, and D. J. Singh. Spin-Lattice Coupling and Superconductivity in Fe Pnictides. *Adv. Cond. Matt. Phys.*, 2010:164916, 2010.